

...MAN - ALPACA FIBRE ANALYSIS

Client Lofty Ridge Farm PO Box 71 Mount Pleasant SA 5235

Date Sample Taken -

Wool Growth -

KAIA 2023

Contact :- Micron Man Our Phone (08)94181733 P.O. Box 1423 Bibra Lake W.A. 6965

Group ID. FULL GROUP T HIGH ON

Test No. LRF40207

months Age at Sample Date months

Eartag:

Micron Deviation: -4.9 mic

0.0 %

>30:

3.9 mic SD 24.2 % CV CE 1.5 % SF 16.1 mic 100.0 % CF

Micron:


CRV 28.8 Deg/mm 24.5 Deg/mm SDC

16.1 mic

Micron Profile Graph

Total Fibres counted: 2552

OFDA2000 Alpaca Calibration : Trim High

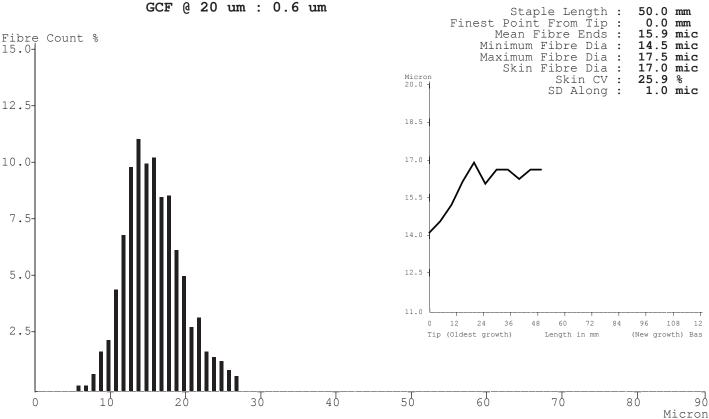

EXPLANATION OF TERMS

- FD : Overall average Fibre Diameter measured in micron.
- Standard Deviation, measures the distance either side of the average fibre diameter where approx 2/3 of the fibre diameters lie.
- Coefficient of Variation = SD as a percentage of the average micron CE: Coarse Edge. The percentage of fibres that lie over 10 microns greater than the average fibre diameter.
- ${\tt CF}$: Comfort Factor. The percentage of fibres less than 30 microns
- Spinning Fineness. Combine Micron & CV to a single number to represent the spinning quality expressed in microns.
- The percentage of fibres greater than 30 microns. >30 :

- CRV: Fibre Curvature is the average curvature or bending over one millimetre length. It is related to crimp frequency and is measured in degrees per millimetre (Dg/mm).

 SDC: Standard Deviation of Curvature is the variation of curvature for the above measurement. SDC is related to crimp definition and measured in degrees per millimetre (Dg/mm).
- If sample is tested with Trim High ON, then the result is trimmed to 4 SD's above average FD. If sample average FD=22um and SD=5um then Trim High ON = 22+20=44um. Measurement above 44um is removed. Trim High OFF means no coarse tail trimming on the sample tested that gives a closer result to other instruments.
 - GCF: Grease Correction Factor is the FD adjustment needed when measuring greasy Alpaca fibre @ 20um-0.6um = 19.4um.